


Diffraction

Scattering amplitude

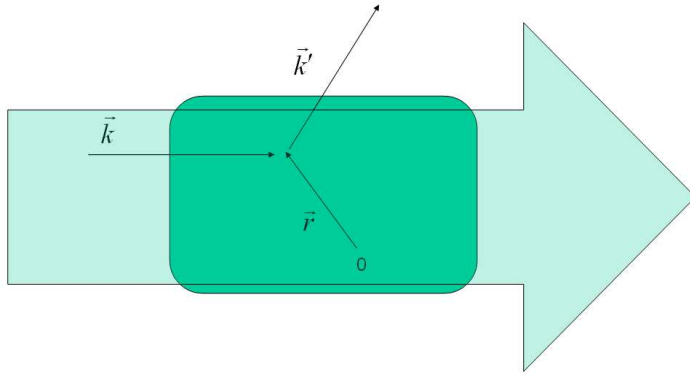

$$F \propto \int n(\vec{r}) \exp(-i\Delta\vec{k} \cdot \vec{r}) dV$$

expand $n(r)$ in a Fourier series

$$n(\vec{r}) = \sum_{\vec{G}} n_{\vec{G}} \exp(i\vec{G} \cdot \vec{r})$$

$$F \propto \sum_{\vec{G}} \int n_{\vec{G}} \exp(i(\vec{G} - \Delta\vec{k}) \cdot \vec{r}) dV$$


if $\vec{G} = \Delta\vec{k}$, all components add coherently

diffraction condition: $\vec{G} = \Delta\vec{k}$

The intensity of the peak at G is $|n_G|^2$

nobel prize 1914

first diffraction experiment of Max von Laue 1912
ZnS single crystal, exposure time 30'
the 5th diffraction pattern

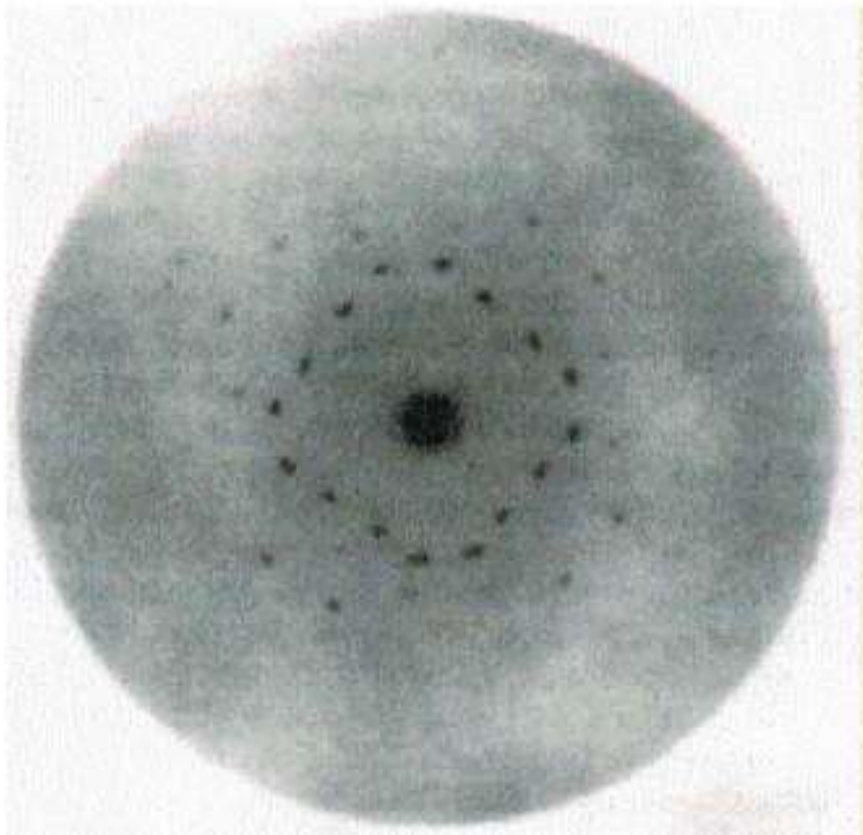


M. von Laue (1879-1960)


$$\vec{G} = \Delta\vec{k}$$

Diffraction condition (Laue condition)

$$\vec{k}' - \vec{k} = \Delta\vec{k} = \vec{G}$$

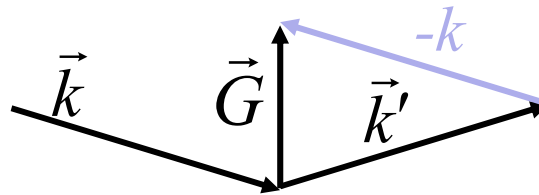


$$|\vec{k}| = |\vec{k}'| \text{ for elastic scattering}$$

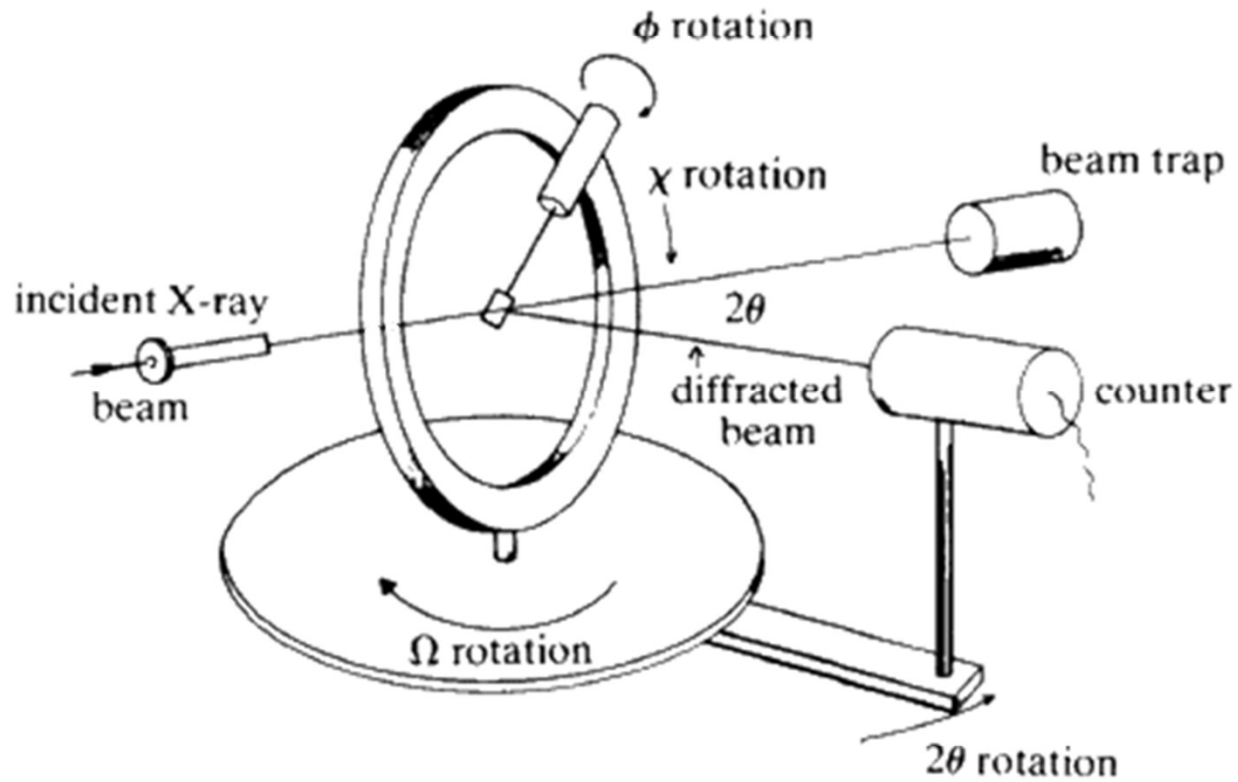

θ sets the length of the scattering vector

Single crystal diffraction

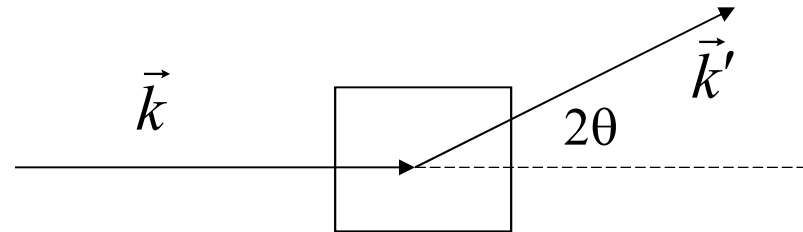

$$\vec{G} = \Delta\vec{k} = \vec{q} \quad \leftarrow \text{Scattering wave vector}$$

Every time a diffraction peak is observed, record G . When many G vectors are known, determine the reciprocal lattice.

The sample and the detector must be turned to find all of the diffraction peaks.

G_x	G_y	G_z	$ n_G ^2$
2.4E10	2.4E10	0	10341
2.4E10	0	2.4E10	9989

$$n(\vec{r}) = \sum_{\vec{G}} n_{\vec{G}} \exp(i\vec{G} \cdot \vec{r})$$

Determining real space primitive lattice vectors

$$\vec{a}_1 = 2\pi \frac{\vec{b}_2 \times \vec{b}_3}{\vec{b}_1 \cdot (\vec{b}_2 \times \vec{b}_3)}$$

$$\vec{a}_i \cdot \vec{b}_j = 2\pi \delta_{ij}$$

$$\vec{a}_2 = 2\pi \frac{\vec{b}_3 \times \vec{b}_1}{\vec{b}_1 \cdot (\vec{b}_2 \times \vec{b}_3)}$$

$\vec{b}_1, \vec{b}_2, \vec{b}_3$ determined
from diffraction experiment

$$\vec{a}_3 = 2\pi \frac{\vec{b}_1 \times \vec{b}_2}{\vec{b}_1 \cdot (\vec{b}_2 \times \vec{b}_3)}$$

Volume of the primitive unit cell $\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)$


G vectors specify the Bravais lattice.

X-ray Fluorescence spectrometer



Tells you the atomic composition of a sample to a few %

Ewald sphere $\Delta\vec{k} = \vec{G}$

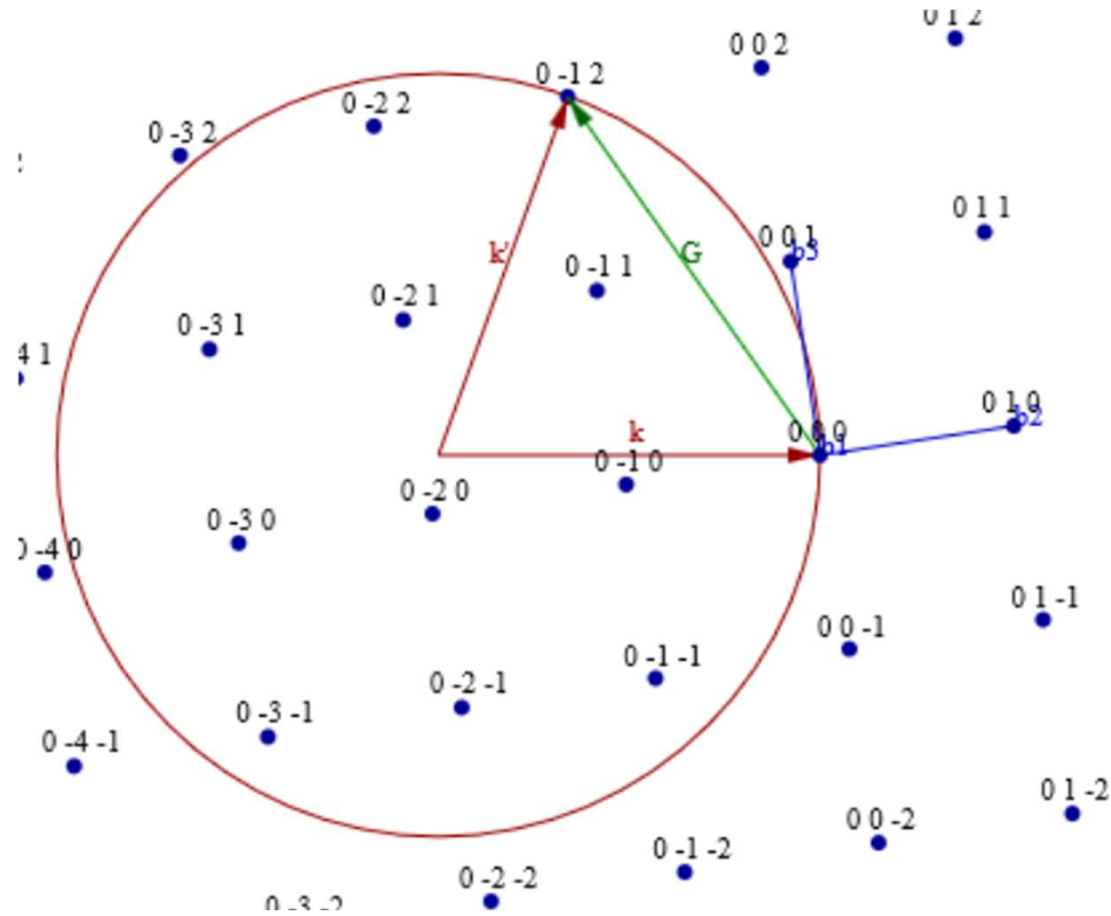

Draw a vector representing the incoming radiation so that it ends at the origin. As the crystal is rotated around the origin, the condition for diffraction will be satisfied every time a reciprocal lattice point is on the sphere.

The number of diffraction peaks that will be observed in a diffraction experiment

Diffraction can occur whenever the diffraction condition, $\vec{k}' - \vec{k} = \vec{G}$, is satisfied. Here \vec{k} is the wave vector of the incoming waves, \vec{k}' is the wave vector of the scattered wave, and \vec{G} is a reciprocal lattice vector. For elastic scattering, $|\vec{k}| = |\vec{k}'|$ and diffraction can only occur for $2|\vec{k}| > |\vec{G}|$. Thus, there are only a finite number of diffraction peaks observable. The number of diffraction peaks can be estimated by dividing the volume of a sphere of radius $2|\vec{k}|$ by the volume of a primitive unit cell in reciprocal space. A more exact number can be obtained by testing if reciprocal lattice points lie inside the sphere. The form below calculates the primitive lattice vectors in reciprocal space from the primitive lattice vectors in real space and then determines the number of reciprocal lattice points that satisfy the diffraction condition.

Primitive lattice vectors:

$\vec{a}_1 =$ $\hat{x} +$ $\hat{y} +$ \hat{z} [Å]
 $\vec{a}_2 =$ $\hat{x} +$ $\hat{y} +$ \hat{z} [Å]
 $\vec{a}_3 =$ $\hat{x} +$ $\hat{y} +$ \hat{z} [Å]

X-ray wavelength $\lambda =$ [Å]

= 1.540598 Å
 = 2.28975 Å
 = 0.7093165 Å


Primitive reciprocal lattice vectors

$$\vec{b}_1 = 2\pi \frac{\vec{a}_2 \times \vec{a}_3}{\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)} = 1.525 \hat{k}_x + 0.000 \hat{k}_y + 0.000 \hat{k}_z [\text{Å}^{-1}]$$

$$\vec{b}_2 = 2\pi \frac{\vec{a}_3 \times \vec{a}_1}{\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)} = 0.000 \hat{k}_x + 1.525 \hat{k}_y + 0.000 \hat{k}_z [\text{Å}^{-1}]$$

$$\vec{b}_3 = 2\pi \frac{\vec{a}_1 \times \vec{a}_2}{\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)} = 0.000 \hat{k}_x + 0.000 \hat{k}_y + 1.525 \hat{k}_z [\text{Å}^{-1}]$$

Diffraction condition

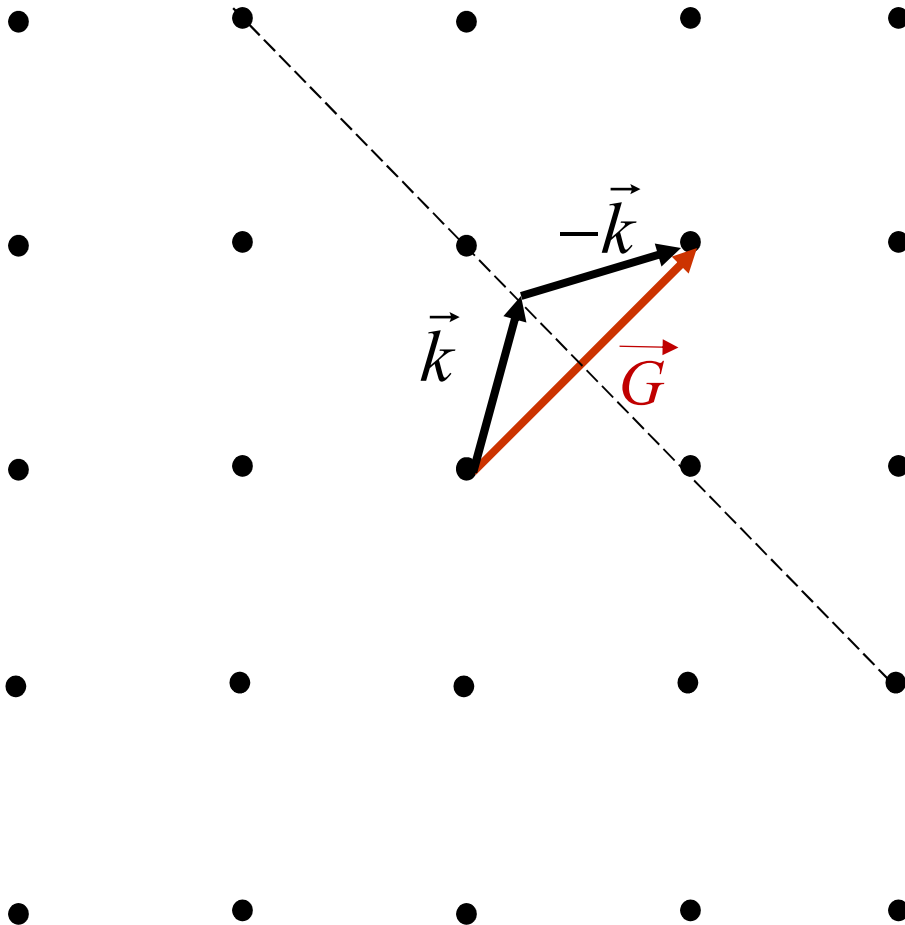

$$\vec{k}' - \vec{k} = \vec{G}$$

For every G there is a $-G$ so the diffraction condition can also be written as


$$\vec{k} - \vec{k}' = \vec{G}$$

A wave will be diffracted if the wave vector ends on one of the planes.
The wavelength changes when you change k .

Brillouin zones




Leon Brillouin

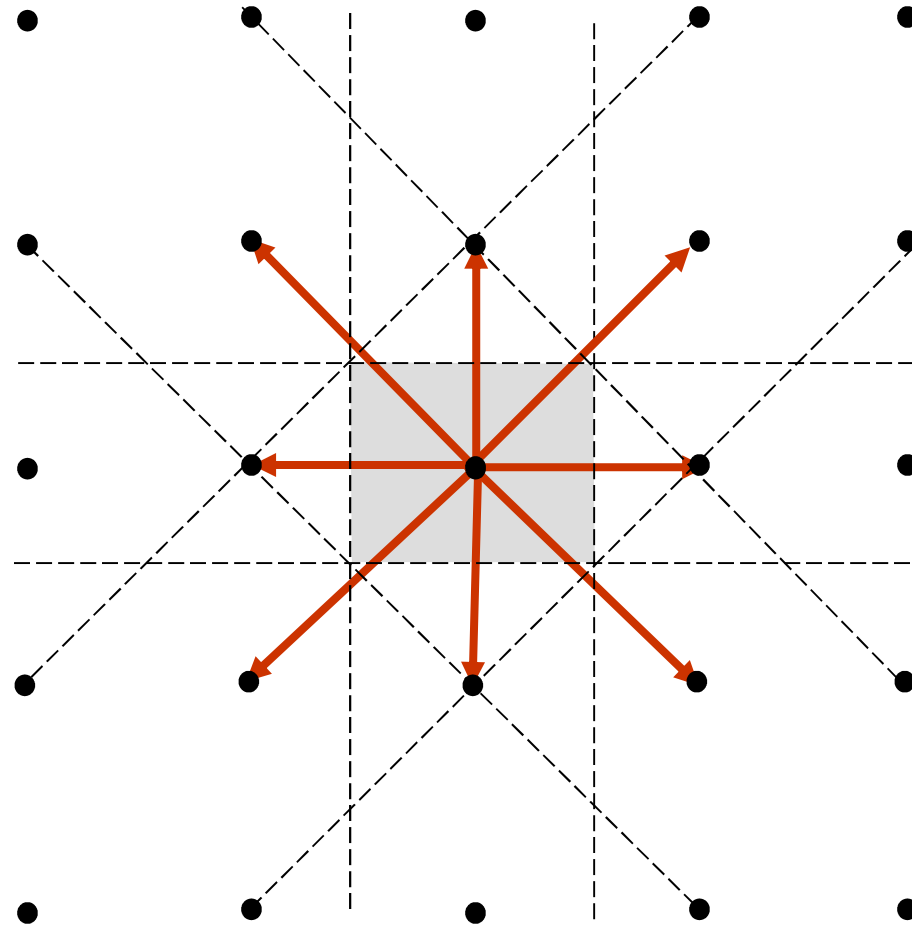


1st Brillouin zone consists of the k -states around the origin that can be reached without crossing a plane.


1st Brillouin zones

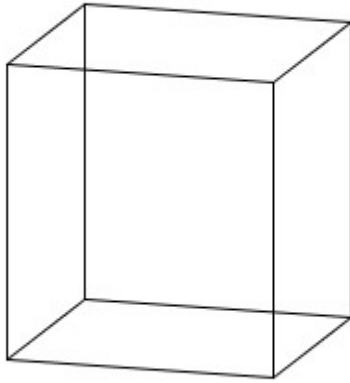

sc

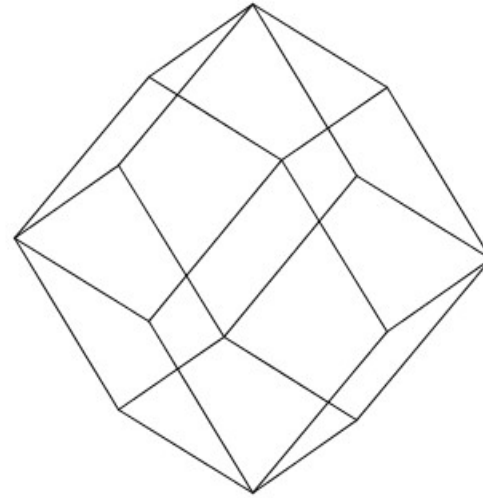








bcc

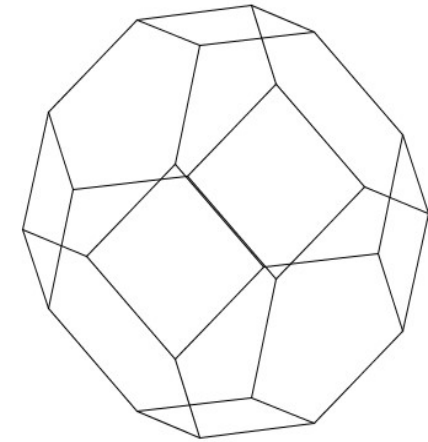


fcc

1st Brillouin is the Wigner-Seitz cell in reciprocal space.

Brillouin zones
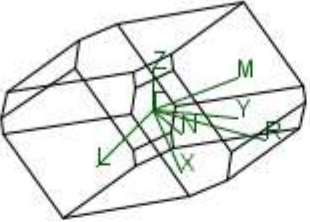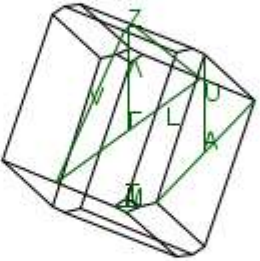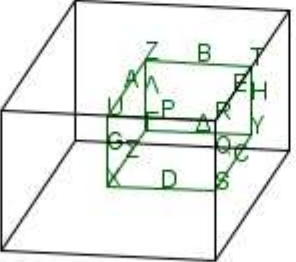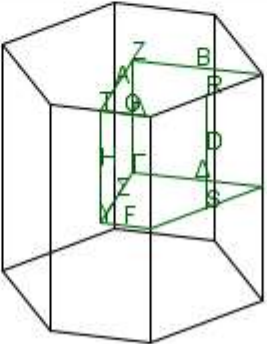
<p>Triclinic</p> <p>$a \neq b \neq c$ $\alpha \neq \beta \neq \gamma$</p>	 <p>Triclinic</p>	
<p>Monoclinic</p> <p>$a \neq b \neq c$ $\alpha \neq 90^\circ$ $\beta = \gamma = 90^\circ$</p>	 <p>Monoclinic simple</p>	 <p>Monoclinic Base centered</p>
<p>Orthorhombic</p> <p>$a \neq b \neq c$ $\alpha = \beta = \gamma = 90^\circ$</p>	 <p>Orthorhombic simple</p>	 <p>Base centered</p>
		

Electron density of an atom

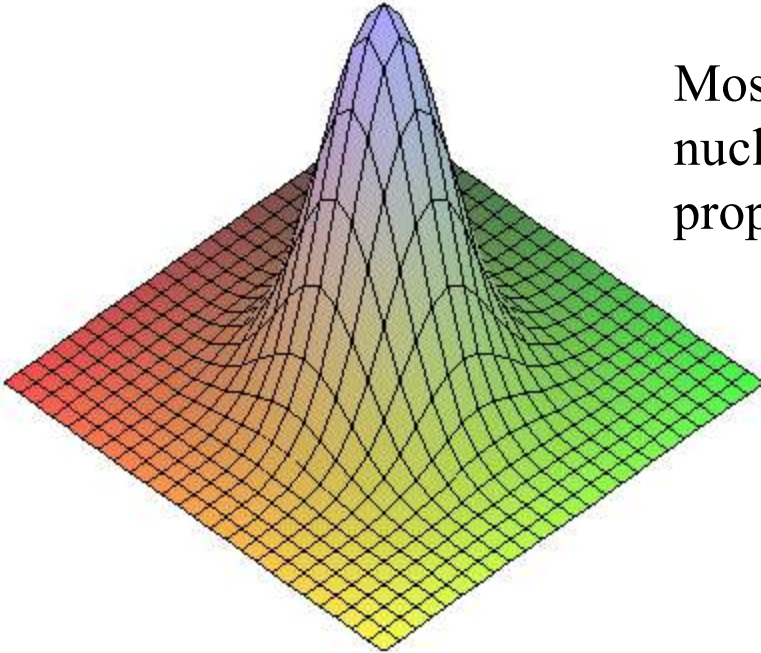

Most of the electrons are concentrated around the nucleus. The integral over the electron density is proportional to the number of electrons.

$$n_j(\vec{r}) \propto \exp\left(-\frac{(\vec{r} - \vec{r}_j)^2}{r_0^2}\right)$$

Approximately a Gaussian centered at r_j

Electron density

Write the electron density as a Fourier series

$$n(\vec{r}) = \sum_{\vec{G}} n_{\vec{G}} e^{i\vec{G}\cdot\vec{r}} = \sum_{\vec{T}} \sum_j n_j \left(\vec{r} - \vec{r}_j + \vec{T} \right),$$

position of atom j of the basis

Translation vector

Multiply by $e^{-i\vec{G}'\cdot\vec{r}}$ and integrate over a unit cell.

$$\sum_{\vec{G}} \int_{\text{u.c.}} n_{\vec{G}} e^{i\vec{G}\cdot\vec{r}} e^{-i\vec{G}'\cdot\vec{r}} d\vec{r} = \sum_j \int_{\text{u.c.}} n_j (\vec{r} - \vec{r}_j) e^{-i\vec{G}'\cdot\vec{r}} d\vec{r}.$$

1

Electron density

$$n_{\vec{G}}V = \sum_j \int n_j(\vec{r} - \vec{r}_j) e^{-i\vec{G}\cdot\vec{r}} d\vec{r}.$$

Make a substitution $\vec{r}' = \vec{r} - \vec{r}_j$.

$$n_{\vec{G}} = \frac{1}{V} \sum_j e^{-i\vec{G}\cdot\vec{r}_j} \underbrace{\int n_j(\vec{r}') e^{-i\vec{G}\cdot\vec{r}'} d\vec{r}'}.$$

Fourier transform of the electron density of atom j
= atomic form factor $f_j(|G|)$

Atomic form factor

$$f_j(\vec{G}) = \int n_j(\vec{r}) e^{-i\vec{G}\cdot\vec{r}} d\vec{r},$$

The atomic form factors can be looked up in a table.

The structure factors are given in terms of the atomic form factors.

$$n_{\vec{G}} = \frac{1}{V} \sum_j f_j(\vec{G}) e^{-i\vec{G}\cdot\vec{r}_j}$$

sum over the basis

position of atom j of the basis

**International
Tables for
Crystallography
Volume C**

Mathematical, physical and
chemical tables

Edited by E. Prince

eISBN 978-1-4020-5408-2

© International Union of Crystallography
2006

[pdf](#) | [chapter contents](#) | [chapter index](#) | [related articles](#)

International Tables for Crystallography (2006). Vol. C, ch. 4.3, p. 262

Section 4.3.2. Parameterizations of electron atomic scattering factors

J. M. Cowley,^{b†} L. M. Peng,ⁱ G. Ren,^j S. L. Dudarev^c and M. J. Whelan^c

$$\vec{k}' - \vec{k} = \vec{q} = \vec{G}$$

Table 4.3.2.2 | pdf |

Elastic atomic scattering factors of electrons for neutral atoms and s up to 2.0 Å⁻¹

$$f(q) = \sum_i a_i \exp(-b_i q^2)$$

Element	Z	a ₁	a ₂	a ₃	a ₄	a ₅	b ₁	b ₂	b ₃	b ₄	b ₅
H	1	0.0349	0.1201	0.1970	0.0573	0.1195	0.5347	3.5867	12.3471	18.9525	38.6269
He	2	0.0317	0.0838	0.1526	0.1334	0.0164	0.2507	1.4751	4.4938	12.6646	31.1653
Li	3	0.0750	0.2249	0.5548	1.4954	0.9354	0.3864	2.9383	15.3829	53.5545	138.7337
Be	4	0.0780	0.2210	0.6740	1.3867	0.6925	0.3131	2.2381	10.1517	30.9061	78.3273
B	5	0.0909	0.2551	0.7738	1.2136	0.4606	0.2995	2.1155	8.3816	24.1292	63.1314
C	6	0.0893	0.2563	0.7570	1.0487	0.3575	0.2465	1.7100	6.4094	18.6113	50.2523
N	7	0.1022	0.3219	0.7982	0.8197	0.1715	0.2451	1.7481	6.1925	17.3894	48.1431
O	8	0.0974	0.2921	0.6910	0.6990	0.2039	0.2067	1.3815	4.6943	12.7105	32.4726
F	9	0.1083	0.3175	0.6487	0.5846	0.1421	0.2057	1.3439	4.2788	11.3932	28.7881
Ne	10	0.1269	0.3535	0.5582	0.4674	0.1460	0.2200	1.3779	4.0203	9.4934	23.1278
Na	11	0.2142	0.6853	0.7692	1.6589	1.4482	0.3334	2.3446	10.0830	48.3037	138.2700
Mg	12	0.2314	0.6866	0.9677	2.1882	1.1339	0.3278	2.2720	10.9241	39.2898	101.9748
Al	13	0.2390	0.6573	1.2011	2.5586	1.2312	0.3138	2.1063	10.4163	34.4552	98.5344



513.001 Molecular and Solid State Physics


Atomic form factors

In the range of scattering vectors between $0 < q < 25 \text{ \AA}^{-1}$, the atomic form factor is well approximated by the expression, [1]

$$f(q) = \sum_{i=1}^4 a_i \exp\left(-b_i \left(\frac{q}{4\pi}\right)^2\right) + c,$$

where the values of a_i , b_i , and c are tabulated below. The different atomic form factors for the elements can be plotted using the form below.

Atomic form factor for H

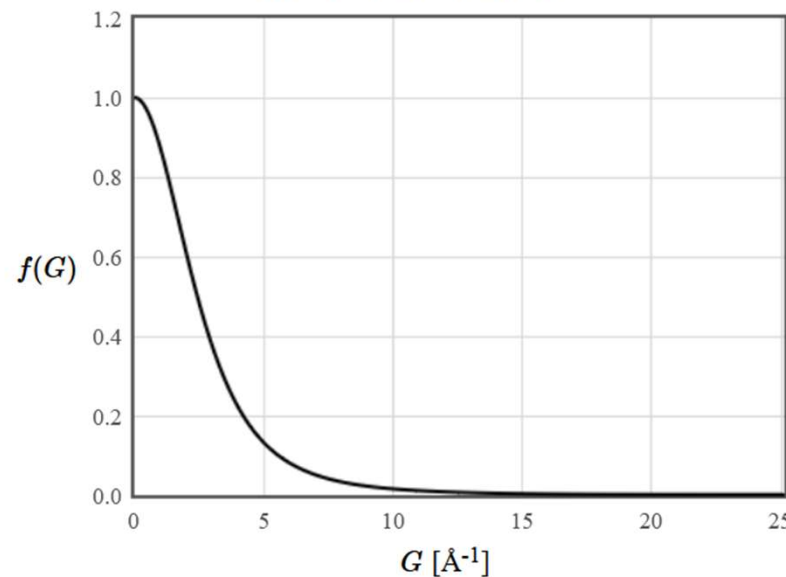

H ▾

$|\vec{G}| =$ \AA^{-1} $f(G) =$

submit

- Home
- Outline
- Introduction
- Molecules
- Crystal Structure
- Crystal Diffraction
- Crystal Binding
- Photons
- Phonons
- Electrons
- Energy bands
- Crystal Physics
- Semiconductors
- Magnetism
- Exam questions
- Appendices
- Lectures
- TUG students
- Student projects
- Skriptum
- Books
- Making presentations

< hide <

Element	a_1	b_1	a_2	b_2	a_3	b_3	a_4	b_4	c
H	0.489918	20.6593	0.262003	7.74039	0.196767	49.5519	0.049879	2.20159	0.001305
H1-	0.897661	53.1368	0.565616	15.187	0.415815	186.576	0.116973	3.56709	0.002389
He	0.8734	9.1037	0.6309	3.3568	0.3112	22.9276	0.178	0.9821	0.0064

Primitive lattice vectors:

$$\vec{a}_1 = 4.12\text{E-}10 \hat{x} + 0 \hat{y} + 0 \hat{z} \text{ [m]}$$

$$\vec{a}_2 = 0 \hat{x} + 4.12\text{E-}10 \hat{y} + 0 \hat{z} \text{ [m]}$$

$$\vec{a}_3 = 0 \hat{x} + 0 \hat{y} + 4.12\text{E-}10 \hat{z} \text{ [m]}$$

Basis:
The positions of the atoms are given in fractional coordinates between -1 and 1.

Cs1+	0	$\vec{a}_1 +$	0	$\vec{a}_2 +$	0	\vec{a}_3
Cl1-	0.5	$\vec{a}_1 +$	0.5	$\vec{a}_2 +$	0.5	\vec{a}_3
		$\vec{a}_1 +$		$\vec{a}_2 +$		\vec{a}_3
		$\vec{a}_1 +$		$\vec{a}_2 +$		\vec{a}_3
		$\vec{a}_1 +$		$\vec{a}_2 +$		\vec{a}_3

submit

Primitive reciprocal lattice vectors

$$\vec{b}_1 = 2\pi \frac{\vec{a}_2 \times \vec{a}_3}{\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)} = 1.525\text{e+}10 \hat{k}_x + 0.000 \hat{k}_y + 0.000 \hat{k}_z \text{ [m}^{-1}\text{]}$$

$$\vec{b}_2 = 2\pi \frac{\vec{a}_3 \times \vec{a}_1}{\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)} = 0.000 \hat{k}_x + 1.525\text{e+}10 \hat{k}_y + 0.000 \hat{k}_z \text{ [m}^{-1}\text{]}$$

$$\vec{b}_3 = 2\pi \frac{\vec{a}_1 \times \vec{a}_2}{\vec{a}_1 \cdot (\vec{a}_2 \times \vec{a}_3)} = 0.000 \hat{k}_x + 0.000 \hat{k}_y + 1.525\text{e+}10 \hat{k}_z \text{ [m}^{-1}\text{]}$$

Structure factors

The value of $|n_{\vec{G}}|$ for the 000 diffraction peak is the total number of electrons in the primitive unit cell. The intensities of the peaks in an x-ray diffraction experiment


hkl	$ \vec{G} \text{ \AA}^{-1}$	$ n_{\vec{G}} $	$ n_{\vec{G}} ^2$	$\text{Re}\{n_{\vec{G}}\}$	$\text{Im}\{n_{\vec{G}}\}$
000	0.000	72.00	5184	72.00	0.000
-100	1.525	34.43	1185	34.43	5.333e-8
0-10	1.525	34.43	1185	34.43	5.333e-8
00-1	1.525	34.43	1185	34.43	5.333e-8
001	1.525	34.43	1185	34.43	-5.333e-8

crystal structure solution

structural solution of the DNA


F.Crick, J.Watson, M.Wilkins

nobel laureate 1962 for medicine

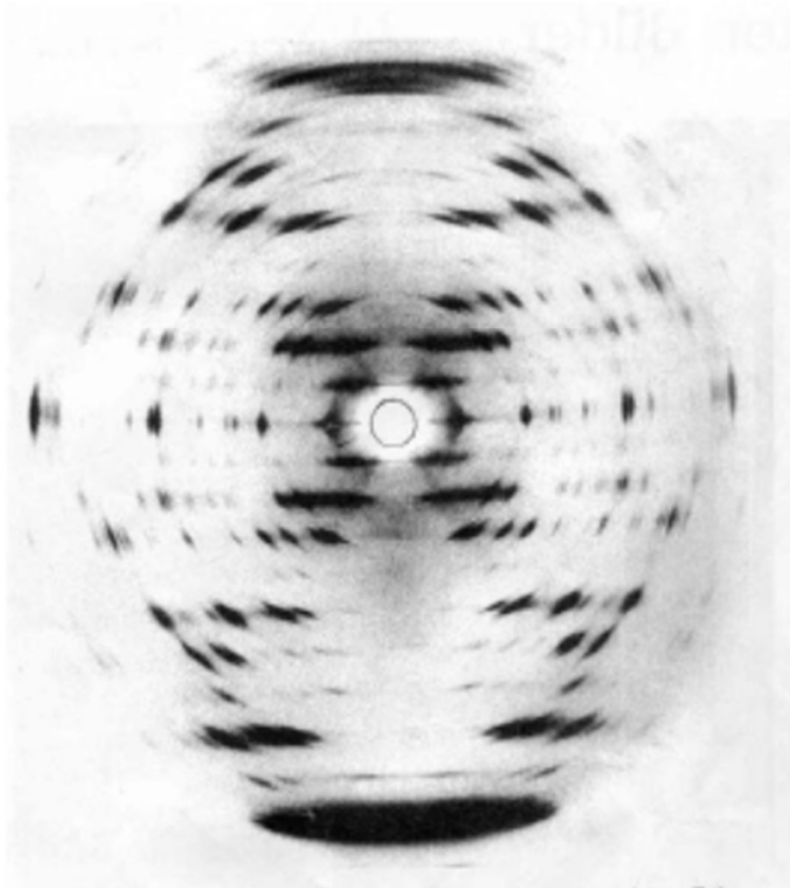

Rosalind Franklin

crystal structure solution

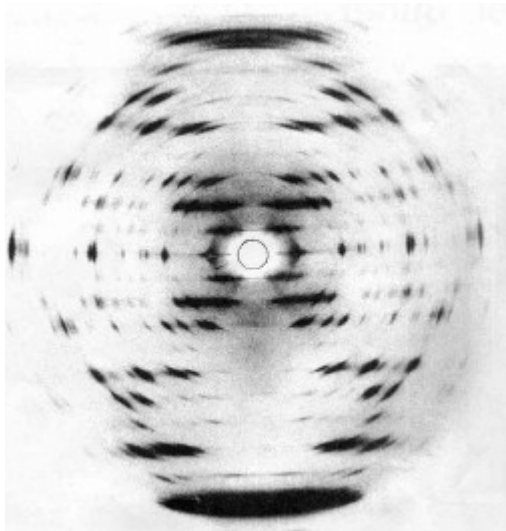

"Guess" the crystal structure




Table 4.3.2.2 | pdf |


Elastic atomic scattering factors of electrons for neutral atoms and s up to 2.0 \AA^{-1}

Element	Z	a_1	a_2	a_3	a_4	a_5	b_1	b_2	b_3
H	1	0.0349	0.1201	0.1970	0.0573	0.1195	0.5347	3.5867	12.3471
He	2	0.0317	0.0838	0.1526	0.1334	0.0164	0.2507	1.4751	4.4938
Li	3	0.0750	0.2249	0.5548	1.4954	0.9354	0.3864	2.9383	15.3829
Be	4	0.0780	0.2210	0.6740	1.3867	0.6925	0.3131	2.2381	10.1517
B	5	0.0909	0.2551	0.7738	1.2136	0.4606	0.2995	2.1155	8.3816
C	6	0.0893	0.2563	0.7570	1.0487	0.3575	0.2465	1.7100	6.4094
N	7	0.1022	0.3219	0.7982	0.8197	0.1715	0.2451	1.7481	6.1925
O	8	0.0974	0.2921	0.6910	0.6990	0.2039	0.2067	1.3815	4.6943
F	9	0.1083	0.3175	0.6487	0.5846	0.1421	0.2057	1.3439	4.2788
Ne	10	0.1269	0.3535	0.5582	0.4674	0.1460	0.2200	1.3779	4.0203
Na	11	0.2142	0.6853	0.7692	1.6589	1.4482	0.3334	2.3446	10.0830
Mg	12	0.2314	0.6866	0.9677	2.1882	1.1339	0.3278	2.2720	10.9241
Al	13	0.2390	0.6573	1.2011	2.5586	1.2312	0.3138	2.1063	10.4163
Si	14	0.2519	0.6372	1.3795	2.5082	1.0500	0.3075	2.0174	9.6746
P	15	0.2548	0.6106	1.4541	2.3204	0.8477	0.2908	1.8740	8.5176
S	16	0.2497	0.5628	1.3899	2.1865	0.7715	0.2681	1.6711	7.0267
Cl	17	0.2443	0.5397	1.3919	2.0197	0.6621	0.2468	1.5242	6.1537
Ar	18	0.2385	0.5017	1.3428	1.8899	0.6079	0.2289	1.3694	5.2561



From the atomic form factors, calculate the structure factors n_G .

Compare $|n_G|^2$ to the measurements



$$n(\vec{r}) = \sum_{\vec{G}} n_{\vec{G}} \exp(i\vec{G} \cdot \vec{r})$$

x-ray diffraction

The shape and the dimensions of the unit cell can be deduced from the positions of the Bragg reflections; the content of the unit cell, on the other hand, must be determined from the intensities of the reflections.

Solid State Physics, Ibach and Lüth


Diffraction condition: $\Delta\vec{k} = \vec{G}$

The intensity of the peaks is proportional to the squared Fourier coefficients of the electron density.

$$n(\vec{r}) = \sum_{\vec{G}} n_{\vec{G}} \exp(i\vec{G} \cdot \vec{r})$$

x-ray diffraction

$$\vec{G}_{hkl} \perp (hkl)$$

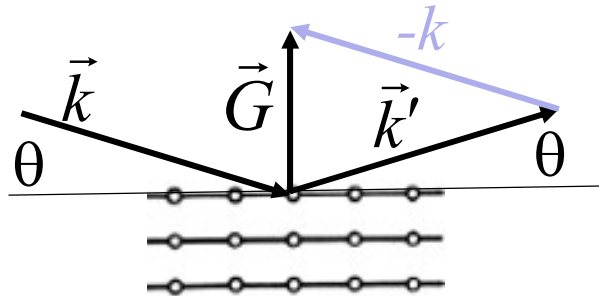



for $\theta = \pi/2$, $2|k| = |G|$ and

constructive interference takes place when $2d_{hkl} = \lambda$.

$$\frac{|\vec{G}_{hkl}|}{2} = \frac{2\pi}{2d_{hkl}} = \frac{2\pi}{\lambda} = |\vec{k}|$$

$$|\vec{G}_{hkl}| = \frac{2\pi}{d_{hkl}}$$


x-ray diffraction

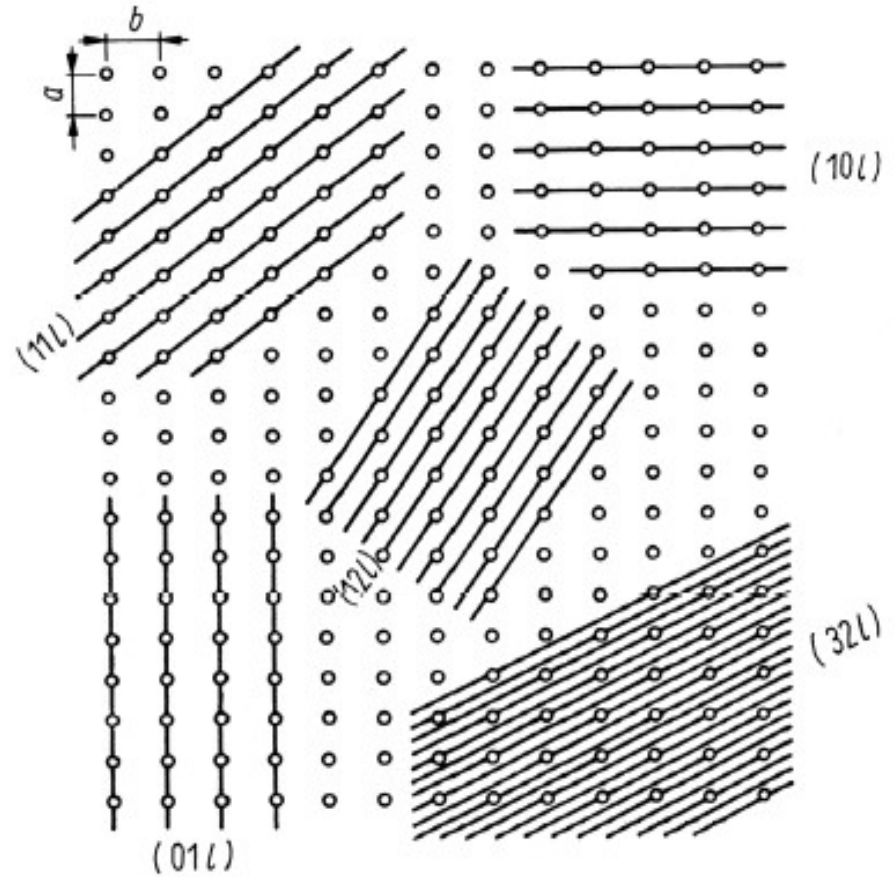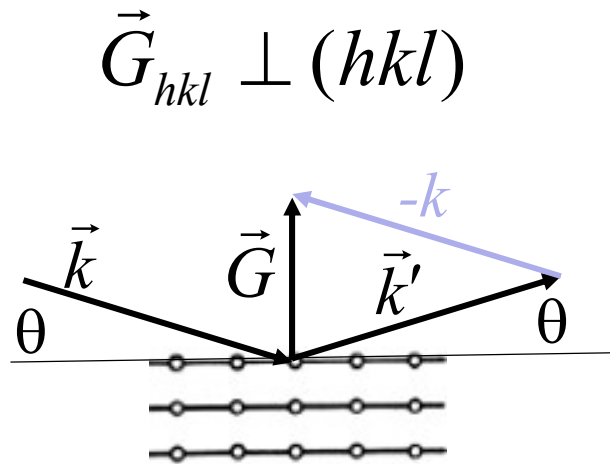

$$|\vec{G}_{hkl}| = \frac{2\pi}{d_{hkl}}$$

distance between the net planes

The reciprocal lattice vector \vec{G}_{hkl} is orthogonal to the (hkl) plane

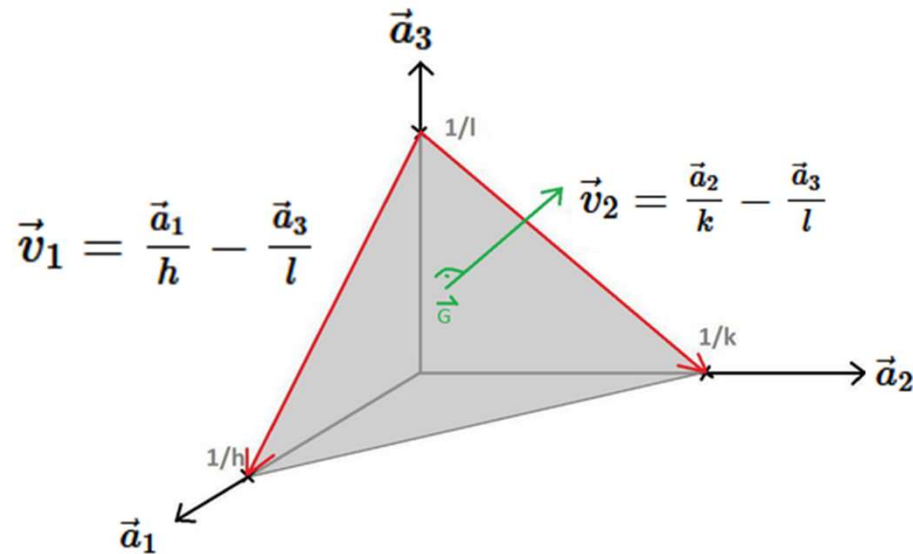

$$\vec{G}_{hkl} = h\vec{b}_1 + k\vec{b}_2 + l\vec{b}_3$$



$$\vec{v}_1 \cdot \vec{G}_{hkl} = \left(\frac{1}{h} h\vec{b}_1 \cdot \vec{a}_1 - \frac{1}{l} l\vec{a}_3 \cdot \vec{b}_3 \right) = 2\pi - 2\pi = 0$$

$$\vec{v}_2 \cdot \vec{G}_{hkl} = \left(\frac{1}{k} k\vec{a}_2 \cdot \vec{b}_2 - \frac{1}{l} l\vec{b}_3 \cdot \vec{a}_3 \right) = 2\pi - 2\pi = 0$$

$$\vec{a}_i \cdot \vec{b}_j = 2\pi\delta_{ij}$$

x-ray diffraction

$$\vec{G}_{hkl} \perp (hkl)$$

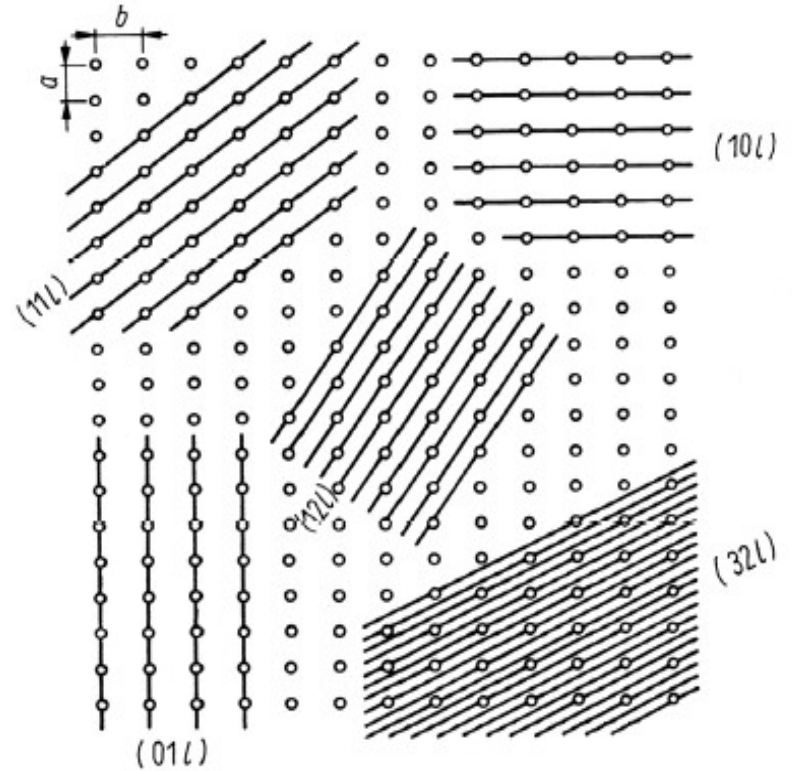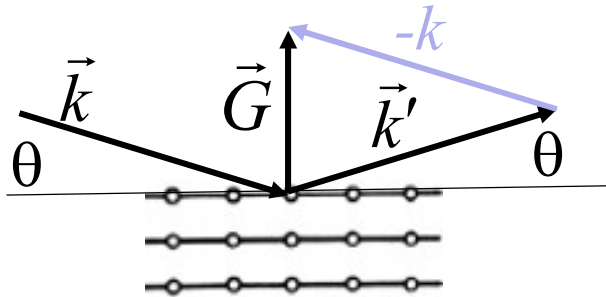

$$|\vec{G}_{hkl}| = |\Delta\vec{k}| = 2|\vec{k}|\sin\theta = \frac{2\pi}{d_{hkl}}$$

$$|\vec{G}_{hkl}| = \frac{2\pi}{d_{hkl}}$$

$$|\vec{k}| = \frac{2\pi}{\lambda}$$

distance between the net planes


$$2d_{hkl} \sin\theta = \lambda \quad \leftarrow \text{another formulation of the diffraction condition}$$

Bragg and Laue conditions

Bragg condition: $2d \sin \theta = n\lambda$

Laue condition: $\Delta \vec{k} = \vec{G} = h\vec{b}_1 + k\vec{b}_2 + l\vec{b}_3$

$2d_{hkl} \sin \theta = \lambda$

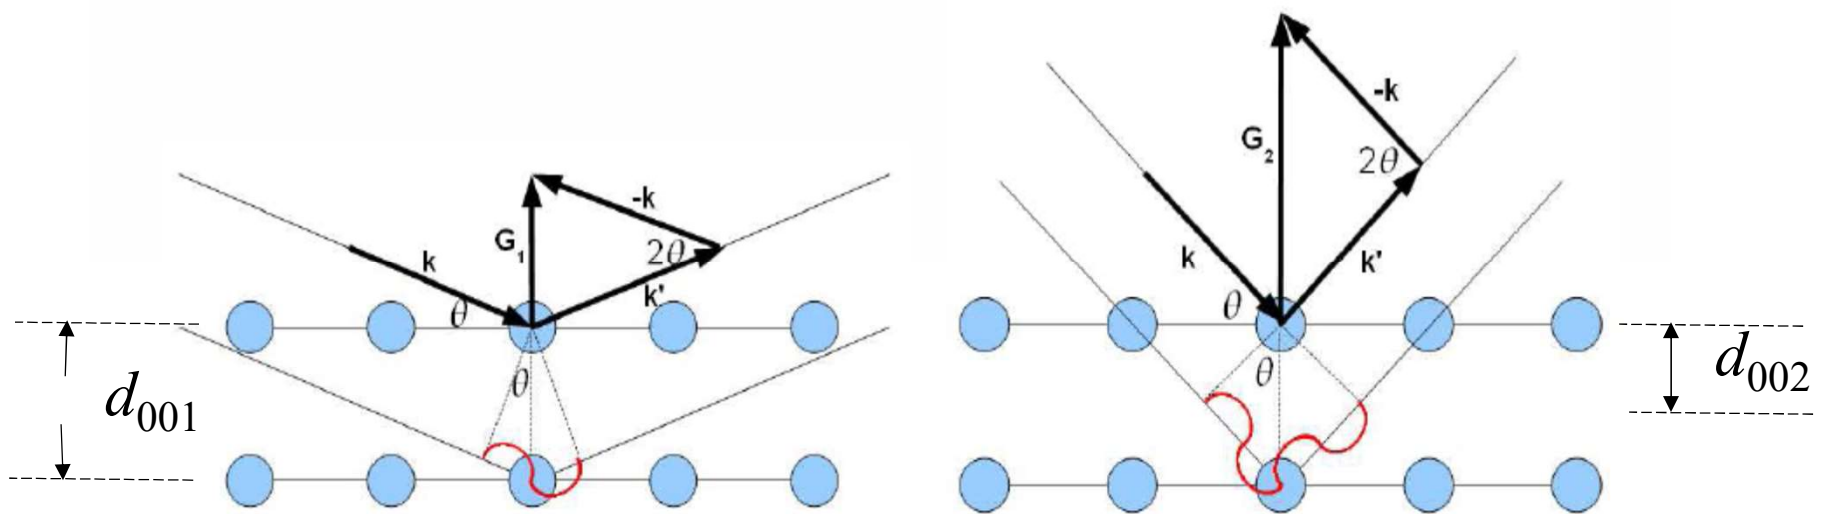


$n = 1 \Leftrightarrow 001$


$n = 2 \Leftrightarrow 002$

Powder diffraction

Powder diffraction is performed on a powder of many small crystals. Ideally, every possible crystalline orientation is represented equally in a powdered sample. The relative intensities of the diffraction peaks indicate which crystal structures are present.

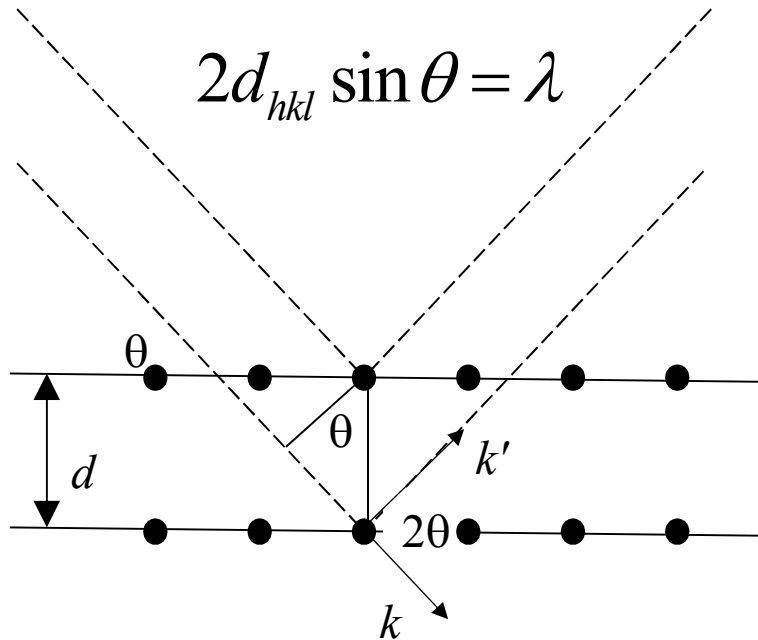


X-rays: Bragg diffraction

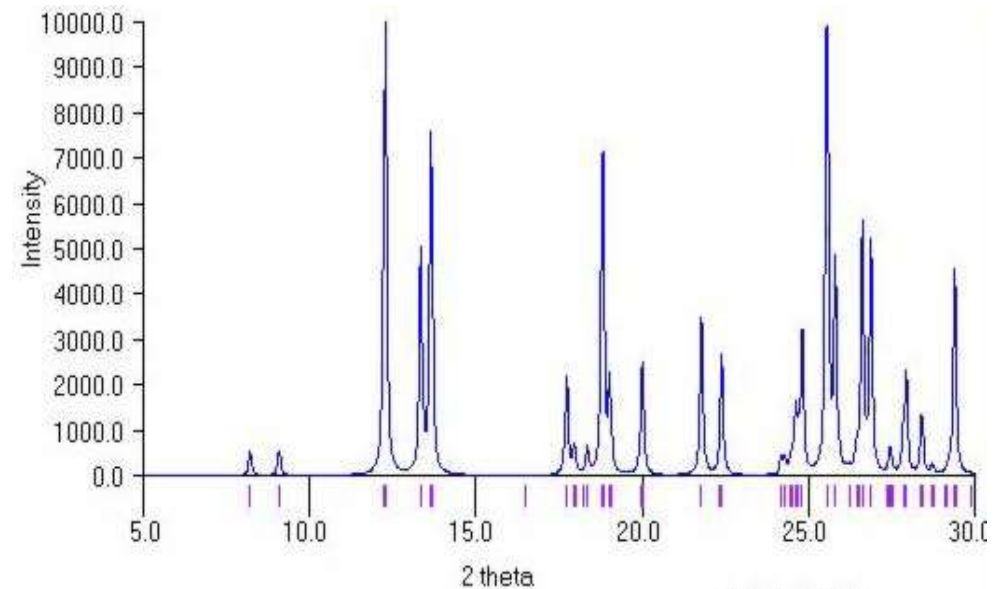


Powder diffraction

For powder diffraction, a crystal is ground into a fine powder so that there are many small crystals with random orientations. X-rays strike the surface of the sample at an angle θ and an x-ray detector is placed at an angle θ to the surface. Only planes parallel to the surface will diffract x-rays to the detector.

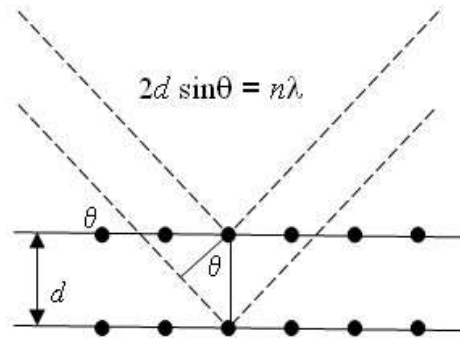

Since there are many small crystals with random orientations in the sample, all possible crystal planes that can diffract the x-rays will contribute to the measured signal when θ satisfies the Bragg condition. The form below can calculate the powder diffraction pattern for any crystal with up to five atoms per primitive unit cell. Some buttons are provided that load the form with the data for certain crystals.

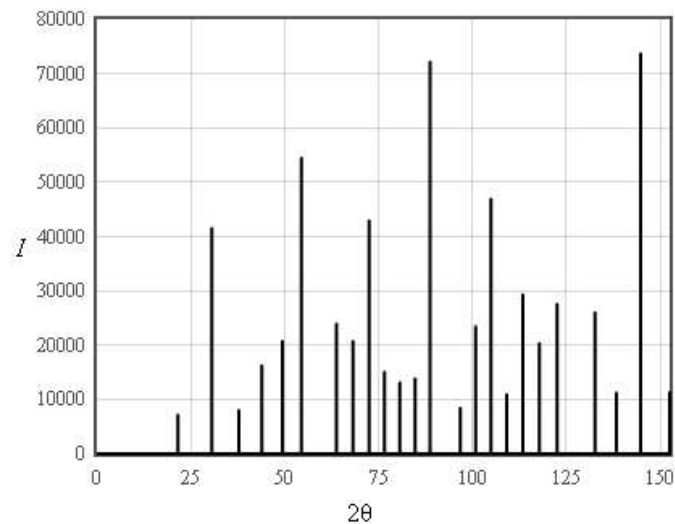

Primitive lattice vectors:

$$\vec{a}_1 = 4.12\text{E-}10 \hat{x} + 0 \hat{y} + 0 \hat{z} \text{ [m]}$$

$$\vec{a}_2 = 0 \hat{x} + 4.12\text{E-}10 \hat{y} + 0 \hat{z} \text{ [m]}$$

$$\vec{a}_3 = 0 \hat{x} + 0 \hat{y} + 4.12\text{E-}10 \hat{z} \text{ [m]}$$

Basis:

The positions of the atoms are given in fractional coordinates between -1 and 1.

Cs ⁺	0	$\vec{a}_1 +$	0	$\vec{a}_2 +$	0	\vec{a}_3
Cl ⁻	0.5	$\vec{a}_1 +$	0.5	$\vec{a}_2 +$	0.5	\vec{a}_3
		$\vec{a}_1 +$		$\vec{a}_2 +$		\vec{a}_3
		$\vec{a}_1 +$		$\vec{a}_2 +$		\vec{a}_3
		$\vec{a}_1 +$		$\vec{a}_2 +$		\vec{a}_3

X-ray wavelength λ [Å] = 1.540598 Cu K α

submit

Al (fcc)

NaCl (fcc)

CsCl (sc)

SrTiO₃ (perovskite, sc)

GaAs (Zincblend, fcc)

GaN (Wurtzite, hex)

http://rruff.geo.arizona.edu/AMS/all_minerals.php


American Mineralogist Crystal Structure Database

Abellaite	Abelsonite	Abenakiite-(Ce)	Abernathyite	Abhurite
Abswurbachite	Acanthite	Acetamide	Acetylene-hydrate	Achavalite
Actinium	Actinolite	Acuminite	Adachiite	Adamantane
Adamantane-methane-hydrate	Adamite	Adamsite-(Y)	Adelite	Admontite
Adolfpateraite	Adranosite	Adranosite-(Fe)	Aegirine	Aenigmatite
Aerinite	Aerugite	Aeschynite-(La)	Aeschynite-(Y)	Afghanite

American Mineralogist Crystal Structure Database

4 matching records for this search.

Aluminium

 Wyckoff R W G

Crystal Structures 1 (1963) 7-83

Second edition. Interscience Publishers, New York, New York

Cubic closest packed, ccp, structure

_database_code_amcsd 0011137

4.04958 4.04958 4.04958 90 90

atom x y z

Al 0 0 0

[Download AMC data \(View Text File\)](#)

[Download CIF data \(View Text File\)](#)



[Download diffraction data \(View Text File\)](#)

[View JMOl 3-D Structure \(pKmalink\)](#)

Aluminium
Wyckoff R W G
Crystal Structures 1 (1963) 7-83
Second edition. Interscience Publishers, New York, New York
Cubic closest packed, ccp, structure
_database_code_amcsd 0011137
CELL PARAMETERS: 4.0496 4.0496 4.0496 90.000 90.000 90.000
SPACE GROUP: Fm3m
X-RAY WAVELENGTH: 1.541838
Cell Volume: 66.409
Density (g/cm3): 2.698
MAX. ABS. INTENSITY / VOLUME**2: 34.61439413
RIR: 4.177
RIR based on corundum from Acta Crystallographica A38 (1982) 733-739
2-THETA INTENSITY D-SPACING H K L Multiplicity
38.50 100.00 2.3380 1 1 1 8
44.76 47.49 2.0248 2 0 0 6
65.16 28.01 1.4317 2 2 0 12
78.30 30.71 1.2210 3 1 1 24
82.52 8.74 1.1690 2 2 2 8

XPOW Copyright 1993 Bob Downs, Ranjini Swaminathan and Kurt Bartelmehs reference, see Downs et al. (1993) American Mineralogist 78, 1104-1107.


Akimotoite
Alabandite
Albite
Alflarsenite
Alinite
Allanite-(La)
Allargentum
Alluaivite
Alnaperboei
Althausite
Alum-(Na)
Aluminoceledonite
Aluminocerite
Aluminotaramite
Aluminum
Alunite
Amarantite
Amarillite
Amesite



copy paper

- Cellulose I_β

- Calcite CaCO₃

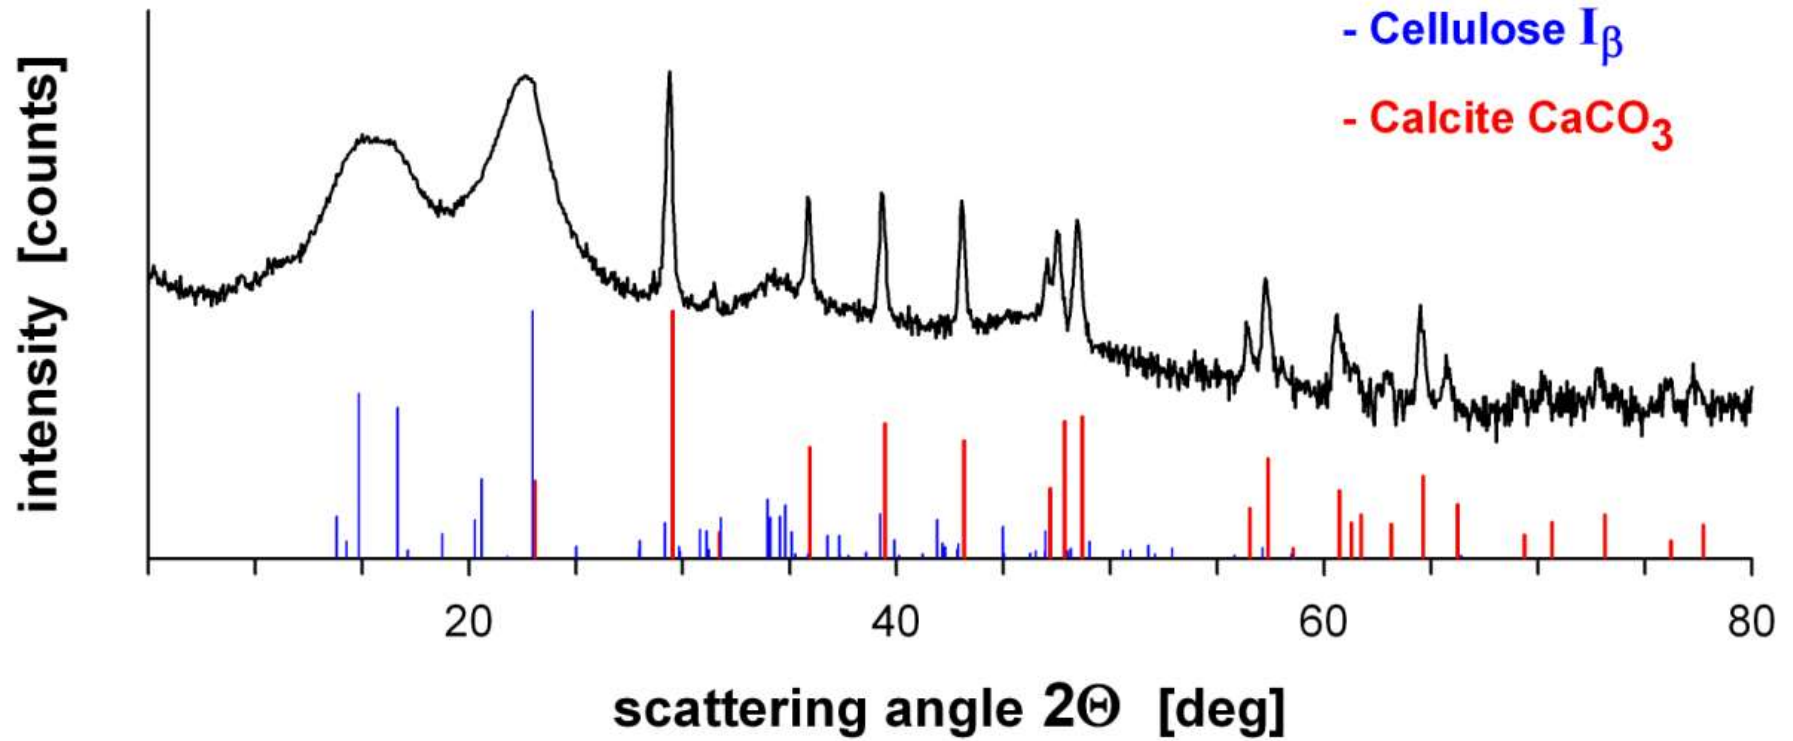

Powder diffraction

Phase identification

Every crystal has a specific "fingerprint" given by the positions and intensities of the diffraction peaks. The composition of a multi-phase specimen can be determined by fitting its diffraction pattern to the diffraction patterns of pure crystals which can be looked up in a database.

International Centre for Diffraction Data www.icdd.com
550,000 reference materials

Phase transitions, thermal expansion, piezoelectricity, piezomagnetism, bulk modulus, compliance tensor can be measured.